

Magnetic order and spin-waves in the quasi-1D $S=1/2$ antiferromagnet $\text{BaCu}_2\text{Si}_2\text{O}_7$

M. Kenzelmann⁽¹⁾, A. Zheludev⁽²⁾, S. Raymond⁽³⁾, E. Ressouche⁽⁴⁾, T. Masuda^(5,6), P. Böni⁽⁷⁾, K. Kakurai⁽⁸⁾, I. Tsukada^(5,9), K. Uchinokura^(5,6) and R. Coldea^(10,11).

(1) *Oxford Physics, Clarendon Laboratory, Oxford OX1 3PU, UK* (2) *Physics Department, Brookhaven National Laboratory, Upton, NY 11973-5000, USA* (3) *CEA-Grenoble, DRFMC/SPSMS/MDN, 38054 GRENOBLE Cedex, FRANCE* (4) *DRFMC/SPSMS/MDN, CENG, 17 rue des Martyrs, 38054 Grenoble Cedex, France* (5) *Department of Applied Physics, The University of Tokyo, 6th Engineering Bldg., 7-3-1 Hongo, Bunkyo-ku, Tokyo 113-8656, Japan* (6) *Department of Advanced Materials Science, The University of Tokyo, 6th Engineering Bldg., 7-3-1 Hongo, Bunkyo-ku, Tokyo 113-8656, Japan* (7) *Laboratory for Neutron Scattering ETH & PSI, CH-5232, Villigen PSI, Switzerland* (8) *Neutron Scattering Laboratory, Institute of Solid State Physics, The University of Tokyo, Tokai, Ibaraki 319-1106, Japan* (9) *Central Research Institute of Electric Power Industry, 2-11-1, Iwato kita, Komae-shi, Tokyo 201-8511, Japan* (10) *Oak Ridge National Laboratory, Solid State Division, Oak Ridge, TN 37831, USA* (11) *ISIS Facility, Rutherford Appleton Laboratory, Oxon OX11 0QX, UK*
(February 1, 2008)

Elastic and inelastic neutron scattering were used to study the ordered phase of the quasi-one-dimensional spin-1/2 antiferromagnet $\text{BaCu}_2\text{Si}_2\text{O}_7$. The previously proposed model for the low-temperature magnetic structure was confirmed. Spin wave dispersion along several reciprocal-space directions was measured and inter-chain, as well as in-chain exchange constants were determined. A small gap in the spin wave spectrum was observed and attributed to magnetic anisotropy effects. The results are discussed in comparison with existing theories for weakly-coupled quantum spin chain antiferromagnets.

PACS numbers: 75.25.+z, 75.10.Jm, 75.40.Gb

I. INTRODUCTION

The investigation of low-dimensional magnets has been a very active research field for the last two decades. First conceived as simple spin models, low-dimensional magnets revealed a far richer physical behaviour than their more conventional three-dimensional (3D) counterparts, due to the importance of quantum fluctuations. Particularly interesting is the one-dimensional (1D) Heisenberg antiferromagnetic model (1D HAF), for which the Hamiltonian is written as

$$H = J \sum_i^{\text{chain}} \mathbf{S}_i \cdot \mathbf{S}_{i+1}, \quad (1)$$

J being the exchange coupling constant. The ground state of the 1D $S=1/2$ HAF is a spin-singlet and can be characterized as “marginal spin liquid”: while long-range order is absent, spatial spin correlations decay according to a power-law, and thus represent quasi-long-range order.¹ The excitation spectrum is isotropic and gapless, and is described in terms of $S = 1/2$ elementary excitations known as “spinons”.² Physical excitations are composed of pairs of spinons, which gives rise to a 2-spinon-continuum.³ This behavior is in stark contrast with that of 3D spin systems, that have long-range order in the ground state (“spin solid”), and where the spectrum is dominated by single-particle $S = 1$ excitations (spin waves). The pure one-dimensional HAF is of course a physical abstraction since spin chains in real materials are always at least weakly coupled. To make a virtue of necessity, weakly coupled antiferromagnetic chains offer the opportunity to study the cross-over from the quantum spin dynamics in a single chain to semi-classical spin waves in 3D systems.

$\text{BaCu}_2\text{Si}_2\text{O}_7$ was recently recognized as an almost ideal model system⁴ for experimental investigation of this dimensional cross-over. The silicate crystallizes in an orthorhombic crystal structure, space group $Pnma$, and the lattice constants are $a = 8.862(2) \text{ \AA}$, $b = 13.178(1) \text{ \AA}$ and $c = 6.897(1) \text{ \AA}$.⁵ The Cu^{2+} -spins are subject to a strong super-exchange interaction via the O^{2-} -ions, producing weakly-coupled antiferromagnetic chains that run along the crystallographic c -axis.⁶ Correspondingly, the magnetic susceptibility shows a broad maximum at around 150 K^4 and its temperature dependence follows the theoretical Bonner-Fisher curve⁷ with an intrachain coupling $J = 24.1 \text{ meV}$. The nearest-neighbor Cu-Cu distance within the chains is equal to $c/2$ (for a schematic view of the crystal structure see Fig. 1 in Tsukada *et al.*⁴). Weak interactions between the chains result in long-range antiferromagnetic ordering at $T_N = 9.2 \text{ K}$, as observed by bulk susceptibility and specific heat measurements.⁴ Preliminary neutron diffraction studies provided an estimate for the ordered magnetic moment at low temperatures: $m_0 = 0.16 \mu_B$.⁴ In the ordered state the spins are aligned along the crystallographic c -axis (chain axis). Early inelastic work suggested that the ratio of inter-chain to in-chain interactions J'/J in $\text{BaCu}_2\text{Si}_2\text{O}_7$ is intermediate compared to that in such well-known $S = 1/2$ systems as KCuF_3 (a more 3D-like material) and Sr_2CuO_3 (an almost perfect 1D compound), as shown in Fig. 1.

In a recent short paper we reported studies of the interplay between single-particle and continuum dynamics in $\text{BaCu}_2\text{Si}_2\text{O}_7$.⁸ For a better quantitative understanding of this behavior a detailed knowledge of both in-chain and inter-chain interactions in this system is required. The present article is a detailed report on neutron scattering characterization of this material. We focus on the 3D as-

pect, namely long-range magnetic order and spin wave-like excitations. From measurements of the spin wave dispersion along different reciprocal-space directions we determine all the relevant parameters of the system, such as the strengths and geometry of inter-chain coupling and magnetic anisotropy.

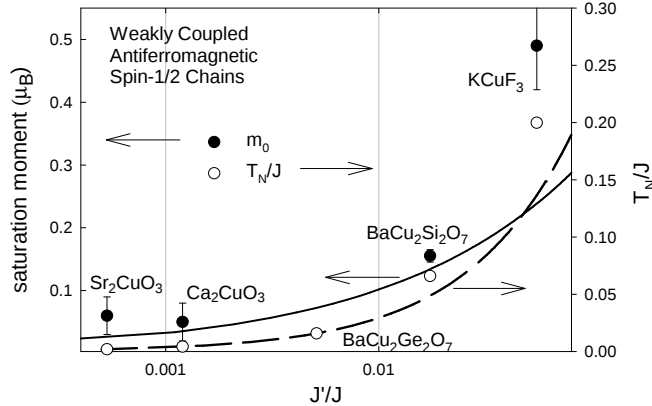


FIG. 1. The ordered moment and T_N/J for the known weakly-coupled antiferromagnetic Heisenberg spin-1/2 chain compounds as a function of $|J'|/J$. For Sr_2CuO_3 ¹⁰, Ca_2CuO_3 ¹⁷ and $\text{BaCu}_2\text{Ge}_2\text{O}_7$ ^{4,11}, $|J'|$ was estimated using the predictions of the chain-mean field model,¹⁵ while actual measured values were used for T_N . For KCuF_3 ^{6,18} $|J'|$ was deduced from spin wave bandwidth perpendicular to the chain axis. The lines are predictions of the chain mean-field model¹⁵.

II. EXPERIMENTAL

Single crystals were grown using the floating-zone technique from a sintered polycrystalline rod. The crystals were carefully checked for twinning because the lattice constants along the a - and c -axis are very similar. The diffraction measurements were performed with a small sample with dimensions 3 mm^3 to exclude sizable extinction effects. The samples used in the inelastic scattering experiments were cylindrical in shape, 5 mm in diameter and 50 mm in height. Up to three single crystals were co-aligned for the different experiments.

The neutron scattering experiments were performed on five different instruments. The two-axis D23 diffractometer at the Institut Laue-Langevin (ILL), Grenoble, France, was used to investigate the ordered magnetic structure at low temperatures (Setup I). D23 is a double-monochromator thermal-neutron diffractometer with a lifting detector arm. The experiment was performed with graphite monochromators and an incident energy $E_i = 14.7\text{ meV}$.

Spin wave dispersion perpendicular to the chain axis was measured using two cold-neutron triple-axis spec-

trometers: the TASP spectrometer at Paul Scherrer Institut (PSI), Villigen, Switzerland (setup II), and the IN14 spectrometer at ILL (Setup III). The zone-boundary energy was measured using the thermal neutron triple-axis spectrometer IN22 at ILL (Setup IV). Preliminary measurements were also performed at the National Institute of Standards and Technology Center for Neutron Research (NCNR).

The experiment on TASP was performed with final neutron energy fixed at $E_f = 8\text{ meV}$. PG(002) reflections were used for monochromator and analyzer. The sample was mounted with its (h, h, l) and $(h, 0, l)$ crystallographic plane in the horizontal scattering plane. The supermirror neutron guides gave a source-to-monochromator collimation of $70'$ both horizontally and vertically. The measurements in the $(h, 0, l)$ -plane were performed using $80'$ - $80'$ collimators before and after the sample and distance collimation after the analyzer. For the measurements in the (h, h, l) -plane, the use of 2 cm wide slits cut the beam divergence before and after the sample down to effective values of $47'$ - $60'$. The energy resolution was 0.38 meV and 0.6 meV for the measurements in the (h, h, l) and $(h, 0, l)$ crystallographic plane, respectively, as determined from the full width at half maximum (FWHM) of the quasi-elastic peak.

For the measurements using IN14 and IN22, PG(002) reflections were used for monochromator and analyzer. The sample was mounted with its $(0, k, l)$ crystallographic plane in the horizontal scattering plane. Final neutron energy was fixed at $E_f = 3\text{ meV}$ and $E_f = 30.5\text{ meV}$, for the IN14 and IN22, respectively, with neutron guides defining the source-to-monochromator collimations of $30'$ and $60'$, respectively. $40'$ - $40'$ collimators were used in both setups before and after the sample, and the use of slits cut the effective collimation of the IN22 setup down to $27'$ - $40'$. The energy resolution (FWHM) was 0.26 meV and 1 meV for the IN14 and IN22 measurements, respectively. Be- or pyrolytic graphite filters were used after the sample to eliminate higher-order beam contamination.

The time-of-flight chopper spectrometer MARI at the ISIS Facility, Rutherford Appleton Laboratory, Oxon, United Kingdom, was used for the measurement of the magnetic excitations in a wide range of wave-vector transfers along the chain (Setup V). The measurements were performed using a chopper-monochromated incident energy $E_i = 30\text{ meV}$ allowing the measurement of the excitation spectrum up to 25 meV. The energy resolution was about 0.35 meV, as determined from the FWHM of the quasi-elastic peak. The resolution of the wave-vector transfer was given by the size of the sample, the detector and their respective distance, and it was typically 0.05 r.l.u. along the chain-axis.

III. MAGNETIC STRUCTURE

To determine the spin structure in the ordered phase, 48 magnetic Bragg intensities were measured at $T = 1.5$ K using Setup I. The main complication in the experiment was that all magnetic reflections appear on top of strong nuclear peaks. The following measurement procedure was implemented. For each reflection the nuclear intensity was measured in a rocking curve at $T = 10$ K $> T_N$. The peak intensity was then measured with high statistics both above and below T_N , and the difference was attributed to magnetic scattering. The integrated magnetic intensity was estimated from the measured intensity ratio and the integrated nuclear intensity. The magnetic structure was found to be totally consistent with that suggested in Tsukada *et al.*⁴ The ordered moment at low temperature $m_0 = 0.15(1)\mu_B$ is parallel to the crystallographic c -axis. Relative nearest-neighbor spin alignment is ferromagnetic along the a -axis and antiferromagnetic along the b - and c -axes, respectively.

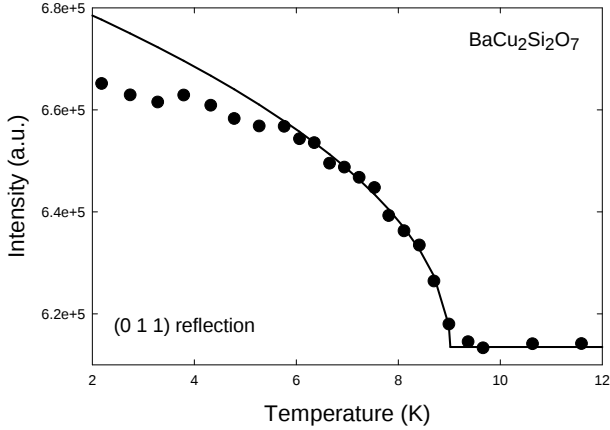


FIG. 2. Temperature dependence of the (0 1 1)-reflection between 1.5 and 15 K. The scattering intensity above $T_N = 9.02$ K comes from the allowed nuclear Bragg reflection at (0 1 1). Below T_N , the intensity increases with decreasing temperature. The solid line is a fit to the data with the critical exponent $\beta = 0.25$ as explained in the text.

The temperature dependence of a few magnetic reflections was measured in the range $T = 1.5$ -15 K as shown in Fig. 2 for the (0 1 1)-peak. Below the ordering temperature T_N , the Bragg intensity increases with decreasing T . The measured peak intensity I is a sum of nuclear and magnetic contributions, the latter being proportional to the square of the sublattice magnetization m . The data were fit to a power-law form:

$$I(T) = I_0 \left(\frac{T_N - T}{T_N} \right)^{2\beta} + N \text{ for } T < T_N, \quad (2)$$

where I_0 is the magnetic intensity at $T = 0$ K, β is the order-parameter critical exponent, and N is the (nu-

clear) scattering intensity assumed to be T -independent. A good fit is obtained with $\beta = 0.25(5)$ and $T_N = 9.0(0.05)$ K. The value of β is clearly below the critical exponent for a 3D antiferromagnet, and is in good agreement with the critical indexes measured in the quasi-1D materials KCuF_3 ⁹ and Sr_2CuO_3 ¹⁰.

IV. DISPERSION OF MAGNETIC EXCITATIONS

A. Dispersion along $[h, 0, 1]$ and $[h, h, 1]$.

Spin wave dispersion at the 1D AF zone-center $q_{\parallel} = \pi$ was measured along the $[1, 0, 0]$ and $[1, 1, 0]$ reciprocal-space directions at $T = 1.5$ K using Setup II. Typical background-subtracted constant- Q scans are shown in Figs. 3 and 4. The background was measured at $Q = (h, 0, 1.25)$ ($h=0-1$) and $Q = (h, h, 1.25)$ ($h=0-1$), where no magnetic scattering is expected in the relevant energy transfer range, due to the steep dispersion along the chain axis. All measured scans show typical spin wave peaks with a sharp onset on the low-energy side, and an extended high-energy resolution tail.

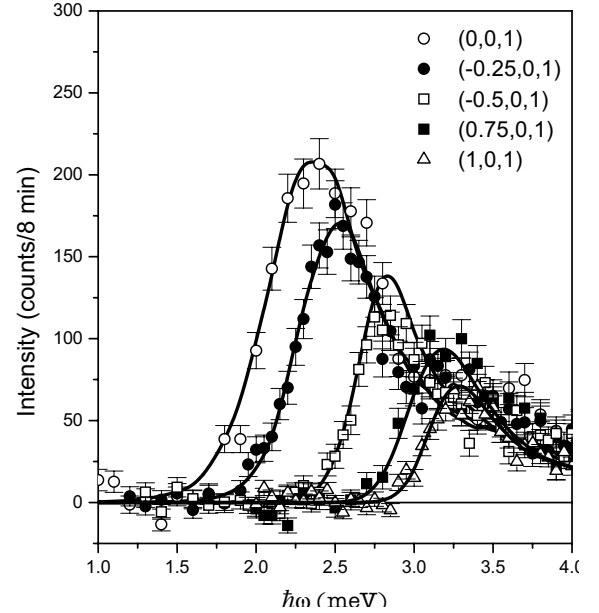


FIG. 3. Constant- Q scans measured at $T = 1.5$ K for three different wave-vector transfers on the $[h, 0, 1]$ reciprocal-space rod (Setup II). The background has been subtracted as described in the text. The solid lines represent global fits to the data using a model SMA cross section function.

The data were analyzed using a model cross-section written in the single-mode approximation (SMA), as will be discussed in detail in section V. The cross section was numerically convoluted with the spectrometer resolution function, calculated in the Cooper-Nathans approximation.¹² Global fits to all data, as well as fits

to individual scans were performed in the energy transfer range 0-4.5 meV. As shown in Figs. 3 and 4, the model used gives an accurate description of the experimentally observed peak shapes. The transverse spin wave dispersion relation deduced from the global fit is shown in Fig. 6 (solid lines), where symbols represent excitation energies obtained in fits to individual scans.

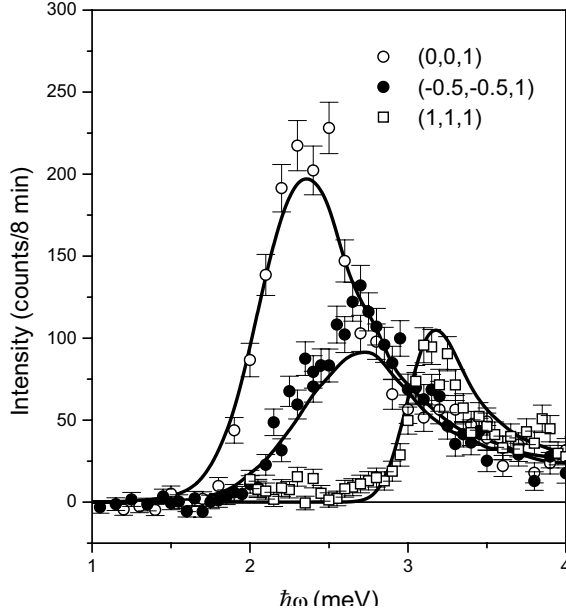


FIG. 4. Constant- Q scans collected at $T = 1.5$ K for three different wave-vector transfers on the $[h, h, 1]$ reciprocal-space rod (Setup II). Background and lines as in Fig. 3.

B. Dispersion along $[0, k, 1]$

Dispersion along the $[0, k, 1]$ -direction was measured using the high-resolution cold-neutron Setup III at $T = 1.5$ K. Constant- Q scans were collected at wave vectors with k in the range $0 \leq k \leq 3$. Some of these data were presented elsewhere.⁸ Scans at the 3D AF zone-centers $(0, 1, 1)$ and $(0, 3, 1)$ (Fig. 5) reveal the presence of a small gap in the spin wave spectrum. In fact, there appear to be two separate modes with slightly different gap energies. These two branches correspond to different polarizations. The relative intensity of the lower-energy excitation at $Q = (0, 3, 1)$ is clearly smaller than at $Q = (0, 1, 1)$. Due to the intrinsic polarization dependence of the magnetic neutron cross section, the observed behavior is consistent with the higher-energy mode being polarized along the a -axis of the crystal, and the lower-energy excitation polarized along b . This consideration is made quantitative by a global fit to all measured scans using an SMA cross section with built-in neutron polarization factors for the two branches (solid lines in Fig. 5).

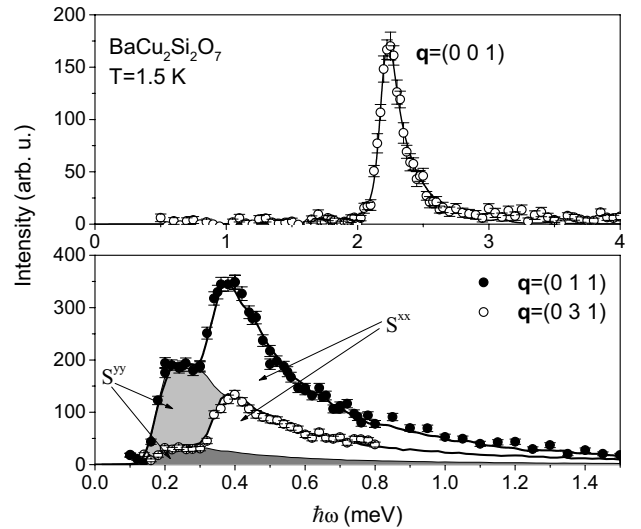


FIG. 5. Constant- Q scans collected at $T = 1.5$ K for $Q = (0, 0, 1)$, $Q = (0, 1, 1)$ and $Q = (0, 3, 1)$ (Setup III). The solid line is a global fit to the data as described in the text. Shaded areas indicate partial contributions of two spin wave branches with different polarization.

The spin wave dispersion relation along the $[0, k, 1]$ reciprocal-space direction is shown in Fig. 6 (solid lines). Here symbols represent fits to individual scans.

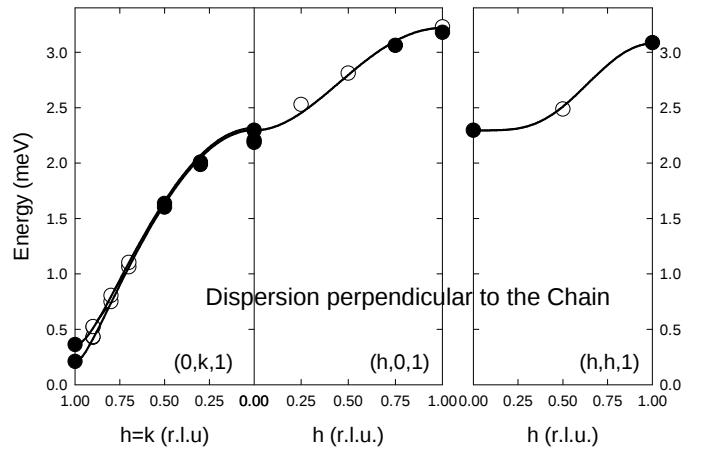


FIG. 6. Dispersion of the spin-wave excitations at $T = 1.5$ K along three different crystallographic directions perpendicular to the chain axis. The open and closed circles show the excitation energies extracted from fits to individual scans. The open circle indicates that the measurements were actually performed at $(0, 1 - k, 1)$, $(-h, 0, 1)$ and $(-h, -h, 1)$, respectively. Error bars are smaller than the symbol size. The solid line is the dispersion determined in a global fit to the data using Eq. 7.

C. Dispersion along the chain axis

The dispersion of magnetic excitations along the chains was previously determined in constant-energy scans up to 16.5 meV energy transfer.⁴ As part of the present work we performed additional measurements of this type using the time-of-flight technique (Setup V). The incident neutron energy at the MARI spectrometer was set to 30 meV and the chain axis was aligned nearly perpendicular to the incoming beam direction. The scattered neutrons were counted by a large array of detectors, arranged in a half circle with radius 4 m vertically below the sample. The energy transfer was determined from the detection time. This allowed a simultaneous measurement of the neutron scattering cross section on a two-dimensional surface in $(\mathbf{Q}, \omega)$ -space. The projection of the measurement surface onto the $(Q_{\parallel}, \omega)$ -plane ($Q_{\parallel}$ being the wave vector transfer along the chain axis) is shown in Fig. 7 for $T=8.5$ K. One clearly sees a “fountain” of magnetic scattering emanating from the $Q_{\parallel} = 2\pi/c$ 1D AF zone-center. We have previously demonstrated that in this energy range both spin waves and continuum contributions to the magnetic dynamic structure factor are important.⁸ However, in the present experiment separating the two does not appear possible due to a poor wave vector resolution (typically 0.05 r.l.u. along the chains). The observed dispersion of magnetic excitations is consistent with the previous estimates of v_s . This is illustrated by the solid line in Fig. 7 that shows the calculated Des Cloizeaux - Pearson SMA dispersion relation for a 1D $S = 1/2$ Heisenberg antiferromagnet,¹³ or the lower bound of the 2-spinon excitation continuum,³ assuming $v_s = 130.5$ meV·Å.

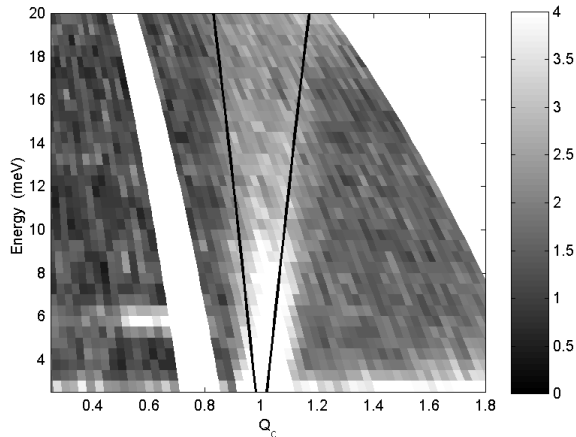


FIG. 7. Neutron scattering intensity measured at 8.5 K using MARI as a function of wave-vector transfer along the chain-axis and energy transfer. The color indicates the measured intensity according to the black and white colorbar on the side. The empty spaces are due to the detector arrangement which is not continuous in the 2Θ scattering angle. The black line is the lower bound of the two spinon continuum for $J = 24.1$ meV.

D. Zone-boundary energy

To verify that only nearest-neighbor in-chain interactions are relevant, the measured value of v_s was compared to the excitation energy at the 1D AF zone-boundary. The latter was measured at $T = 1.5$ K in a constant- Q scan at the wave vector transfer $\mathbf{Q} = (0, 0, 2.5)$ ($Q_{\parallel} = 5\pi/2$), using Setup IV (Fig. 8). The observed peak was analyzed using a Gaussian profile (solid line in Fig. 8) and the zone-boundary energy was determined: $\hbar\omega_{\text{ZB}} = 37.9(0.2)$ meV. With nearest-neighbor spin separation along the chain axis equal to $c/2$, for an $S = 1/2$ 1D AF one expects $\hbar\omega_{\text{ZB}} = \pi J/2$ and $v_s = \pi cJ/4$.¹³ Assuming the nearest-neighbor model, for $\text{BaCu}_2\text{Si}_2\text{O}_7$ we thus obtain $J = 24.1(1)$ meV and $v_s = 130.5(5)$ meV·Å, in excellent agreement with direct spin wave velocity measurements and magnetic susceptibility data.⁴ The agreement suggests that taking into account only nearest-neighbor interactions is indeed an adequate description of the spin chains in $\text{BaCu}_2\text{Si}_2\text{O}_7$.

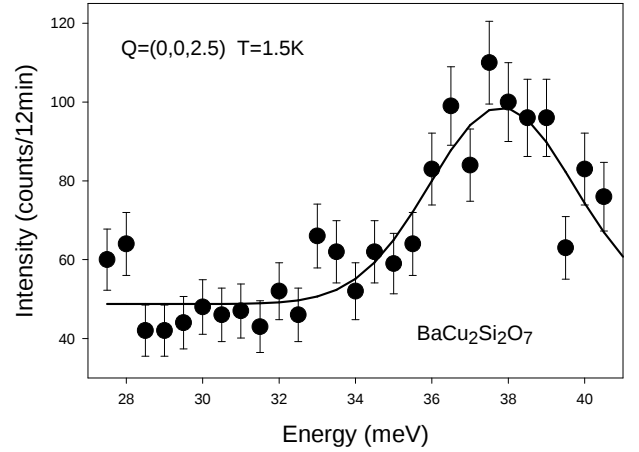


FIG. 8. Constant- Q scan collected at $T = 1.5$ K at the 1D antiferromagnetic zone boundary $\mathbf{Q} = (0, 0, 2.5)$. The solid line is a Gaussian fit to the data.

V. DISCUSSION

Most measurements discussed in this paper have been performed below 4.5 meV, which is the threshold of the excitation continuum.^{8,14} Below this energy, the spectrum is expected to be dominated by single-particle spin wave excitations. The corresponding dynamic structure factor, and the spin wave dispersion relation in particular, can be calculated using the chain-Mean Field (chain-MF) approximation.^{15,16} As will be discussed below, this theoretical construct is in remarkably good quantitative agreement with our experimental results on $\text{BaCu}_2\text{Si}_2\text{O}_7$.

A. Model Hamiltonian

We shall now describe the model Hamiltonian for BaCu₂Si₂O₇ that was used as a starting point in our data analysis. As mentioned above, a single nearest-neighbor Heisenberg exchange coupling constant J is sufficient to describe in-chain interactions. We found that in order to reproduce the observed dispersion in the perpendicular directions, three independent inter-chain exchange constants are required. The Cu²⁺ chains in BaCu₂Si₂O₇ form a rectangular lattice with nearest-neighbor Cu-Cu distances along the a - and b -axes of $a/2$ and $b/2$, respectively. We shall denote the corresponding exchange constants as J_x and J_y . In addition, we shall include exchange interactions along the $[1, 1, 0]$ direction (3rd nearest-neighbor inter-chain Cu-Cu distance) in our model and label the corresponding coupling constant as J_3 . The model Heisenberg Hamiltonian is then written as:

$$H = \sum_i J \mathbf{S}_{\mathbf{r}_i} \mathbf{S}_{\mathbf{r}_i + \mathbf{c}/2} + J_x \mathbf{S}_{\mathbf{r}_i} \mathbf{S}_{\mathbf{r}_i + \mathbf{a}/2} + J_y \mathbf{S}_{\mathbf{r}_i} \mathbf{S}_{\mathbf{r}_i + \mathbf{b}/2} + J_3 \mathbf{S}_{\mathbf{r}_i} \mathbf{S}_{\mathbf{r}_i + \mathbf{a}/2 + \mathbf{b}/2} + J_3 \mathbf{S}_{\mathbf{r}_i} \mathbf{S}_{\mathbf{r}_i + \mathbf{a}/2 - \mathbf{b}/2}. \quad (3)$$

Here the sum is taken over all spins in the system and $\mathbf{r}_i$ is the position of spin i .

Following Schulz¹⁵ and treating the interchain coupling in a mean-field treatment, the Hamiltonian transforms into an effective single-chain Hamiltonian which reads

$$H = \sum_i J \mathbf{S}_i \mathbf{S}_{i+1} - h \sum_i (-1)^i S_i^z - 2N J' m_0^2. \quad (4)$$

The magnetic moment is aligned along the z -axis. Here N is the number of sites in the chain, $m_0 = (-1)^i < S_i^z >$ is the staggered magnetization, and $h = -4J'm_0$. The effective MF inter-chain coupling strength J' for this anisotropic coupling geometry is given by $J' \equiv \frac{1}{4}(2|J_x| + 2|J_y| + 4|J_3|)$.

B. Dynamic structure factor

Essler *et al.* have previously derived the SMA dynamic structure factor for weakly-coupled $S = 1/2$ antiferromagnetic chains in KCuF₃, using the chain-MF/Random Phase Approximation (chain-MF/RPA).¹⁶ It is straightforward to adapt their result to the coupling geometry for the Hamiltonian given in Eq. 3:

$$S^{xx}(\mathbf{Q}, \omega) \propto \frac{1}{\omega_x(\mathbf{Q})} [\delta(\omega - \omega_x(\mathbf{Q})) - \delta(\omega + \omega_x(\mathbf{Q}))], \quad (5)$$

$$S^{yy}(\mathbf{Q}, \omega) \propto \frac{1}{\omega_y(\mathbf{Q})} [\delta(\omega - \omega_y(\mathbf{Q})) - \delta(\omega + \omega_y(\mathbf{Q}))], \quad (6)$$

$$\omega_{x,y}^2(\mathbf{Q}) = \frac{\pi^2}{4} J^2 \sin^2(\pi l) + \frac{\Delta^2}{J_y + 2J_3 - J_x} \times (J_y + 2J_3 - J_x + J(\mathbf{Q})) + D_{x,y}^2. \quad (7)$$

In this formula $S^{xx}(\mathbf{Q}, \omega)$ and $S^{yy}(\mathbf{Q}, \omega)$ are dynamic structure factors for excitations polarized along the a - and b -axes, respectively, and $\mathbf{Q} = (h, k, l)$ is the wave vector transfer. Δ is the gap induced in the quantum spin chains by the effective staggered exchange field in the magnetically ordered state. This gap corresponds to the excitation energy at a point in reciprocal space where inter-chain interactions cancel out at the RPA level, e.g., at $\mathbf{Q} = (0.5, 0.5, 1)$. $J(\mathbf{Q})$ is the Fourier transform of inter-chain coupling, and is given by

$$J(\mathbf{Q}) = J_x \cos(\pi h) + J_y \cos(\pi k) + J_3 \cos(\pi(h + k)) + J_3 \cos(\pi(h - k)). \quad (8)$$

Finally, the parameters D_x and D_y in Eq. 7 are anisotropy gaps for the two spin wave branches, that we empirically include in the dispersion relation, as in Tsukada *et al.*⁴.

The magnetic dynamic structure factor is related to the inelastic neutron scattering cross section through the polarization factors and form factors for the magnetic ions involved:

$$\frac{d\sigma}{d\Omega dE'} \propto |f(\mathbf{Q})|^2 \left[S^{xx}(\mathbf{Q}, \omega) \sin^2(\hat{\mathbf{Q}}, \hat{\mathbf{a}}) + S^{yy}(\mathbf{Q}, \omega) \sin^2(\hat{\mathbf{Q}}, \hat{\mathbf{b}}) \right]. \quad (9)$$

$$S^{yy}(\mathbf{Q}, \omega) \sin^2(\hat{\mathbf{Q}}, \hat{\mathbf{b}}) \right]. \quad (10)$$

The model cross section defined by Eqs. 5-10 were numerically convoluted with the calculated spectrometer resolution function and used in global least-squares fits to the data for each experimental setting. The effective MF inter-chain coupling strength $|J'| \equiv \frac{1}{4}(2|J_x| + 2|J_y| + 4|J_3|)$ is related to the gap energy through $\Delta = 6.175|J'|$.¹⁵ The in-chain exchange constant was fixed at $J = 24.1$ meV, while the parameters J_x , J_y , J_3 , D_x and D_y were refined. The following values were obtained: $J_x = -0.460(7)$ meV (ferromagnetic), $J_y = 0.200(6)$ meV, $2J_3 = 0.152(7)$ meV, $D_x = 0.36(2)$ meV and $D_y = 0.21(1)$ meV. This yields $\Delta = 2.51$ meV and $|J'| = 0.41$ meV. The obtained dispersion relation is shown in Fig. 6 in solid lines. Symbols indicate excitation energies obtained in fits to individual scans.

C. Comparison with the chains-MF model

The chain MF theory does not only reproduce the observed dispersion relation, but is in fact in good quantitative agreement with the data. According to Schulz¹⁵ the relations between m_0 , T_N and $|J'|$ are given by:

$$|J'| = \frac{T_N}{1.28 \sqrt{\ln(5.8J/T_N)}} \quad (11)$$

$$m_0 = 1.017 \sqrt{|J'|/J}. \quad (12)$$

In our case, where $T_N = 9.0$ K and $J = 24.1$ meV, this gives $|J'| = 0.27$ meV and $m_0 = 0.11 \mu_B$. The remaining small discrepancy with experiment can be attributed

to the presence of weak easy-axis (Ising-like) anisotropy, which clearly should have the effect of enhancing long-range order. Indeed, this term, no matter how small, induces long-range order even in the purely 1D model.

VI. CONCLUSION

The obtained detailed characterization of $\text{BaCu}_2\text{Si}_2\text{O}_7$ provides a quantitative basis for the discussion of single-particle vs. continuum excitations in weakly-coupled spin chains in Zheludev *et al.*⁸. The experimental data are remarkably well described by the quantum mean field model.

ACKNOWLEDGMENTS

We would like to thank Dr. L. P. Regnault (CEA Grenoble) and Dr. A. Wildes for their assistance with experiments at ILL, Dr. S.-H. Lee for his assistance with preliminary measurements at NIST, Prof. A. Tsvetik (Oxford University), Prof. R. A. Cowley (Oxford University) and Dr. I. Zaliznyak (BNL) for illuminating discussions, and Mr. R. Rothe (BNL) for technical support. This work is supported in part by the U.S.-Japan Cooperative Program on Neutron Scattering, Grant-in-Aid for COE Research “SCP coupled system” of the Ministry of Education, Science, Sports, and Culture. Work at Brookhaven National Laboratory was carried out under Contract No. DE-AC02-98CH10886, Division of Material Science, U.S. Department of Energy. ORNL is managed for the U.S. D.O.E. by UT-Battelle, LLC, under contract no. DE-AC05-00OR22725. One of the authors (M. K.) is supported by a TMR-fellowship from the Swiss National Science Foundation under contract no. 83EU-053223.

- ⁸ A. Zheludev, M. Kenzelmann, S. Raymond, E. Ressouche, T. Masuda, K. Kakurai, S. Maslov, I. Tsukada, K. Uchinokura, and A. Wildes, *Phys. Rev. Lett.* **85**, 4799 (2000).
- ⁹ D. A. Tennant, S. E. Nagler, D. Welz, G. Shirane, and K. Yamada, *Phys. Rev. B* **52**, 13381 (1995).
- ¹⁰ K. M. Kojima, Y. Fudamoto, M. Larkin, G. M. Luke, J. Merrin, B. Nachumi, Y. J. Uemura, N. Motoyama, H. Eisaki, S. Uchida, K. Yamada, Y. Endoh, S. Hosoya, B. J. Sternlieb, and G. Shirane, *Phys. Rev. Lett.* **78**, 1787 (1997).
- ¹¹ I. Tsukada, J. Takeya, T. Masuda, and K. Uchinokura, *Phys. Rev. B* **62**, R6061 (2000).
- ¹² M. J. Cooper and R. Nathans, *Acta Cryst.* **23**, 357 (1967).
- ¹³ J. des Cloizeaux and J. J. Pearson, *Phys. Rev.* **128**, 2131 (1962).
- ¹⁴ A. Zheludev *et al.*, to be published.
- ¹⁵ H. J. Schulz, *Phys. Rev. Lett.* **77**, 2790 (1996).
- ¹⁶ F. H. L. Essler, A. M. Tsvetik, and G. Delfino, *Phys. Rev. B* **56**, 11001 (1997).
- ¹⁷ K. Yamada, J. Wada, S. Hosoya, Y. Endoh, S. Noguchi, S. Kawamata, and K. Okuda, *Physica* **253C**, 135 (1995).
- ¹⁸ M. T. Hutchings, E. J. Samuelsen, G. Shirane, and K. Hirakawa, *Phys. Rev.* **188**, 919 (1969).

¹ H. A. Bethe, *Z. Phys.* **71**, 205 (1931).

² L. D. Faddeev and L. A. Takhtajan, *Phys. Lett. A* **85**, 375 (1981).

³ G. Müller, H. Thomas, H. Beck, and J. C. Bonner, *Phys. Rev. B* **34**, 1429 (1981).

⁴ I. Tsukada, Y. Sasago, K. Uchinokura, A. Zheludev, S. Maslov, G. Shirane, K. Kakurai, and E. Ressouche, *Phys. Rev. B* **60**, 6601 (1999).

⁵ J. A. S. Oliveira, Ph.D. thesis, Ruprecht-Karls-Universität, Heidelberg, 1993.

⁶ S. K. Satija, J. D. Axe, G. Shirane, H. Yoshizawa, and K. Hirakawa, *Phys. Rev. B* **21**, 2001 (1980).

⁷ J. C. Bonner and M. E. Fisher, *Phys. Rev.* **135**, A640 (1964).